


Instrument Tubing

Quality-assured domestic and non-domestic stainless steel tubing for hydraulic and instrumentation applications



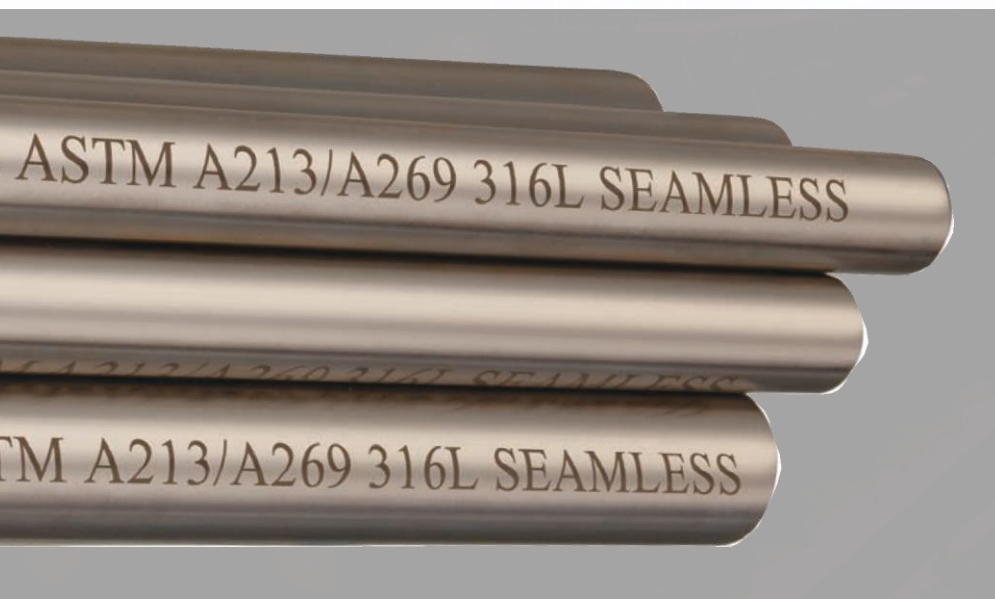

Instrument Tubing Selection Guide

Parker's instrument tube fittings have been designed to work in a wide variety of applications that demand the utmost in product performance.

Although Parker's Instrument tube fittings have been engineered and manufactured to consistently provide this level of reliability, no systems integrity is complete without considering the critical link, tubing.

This booklet is intended to assist the designer to properly select and order quality tubing.

Proper tube selection and installation, we believe, are key ingredients in building leak-free reliable tubing systems.

General Selection Criteria

The most important consideration in the selection of suitable tubing for any application is the compatibility of the tubing material with the media to be contained. Table 1 lists common materials and their associated general application. Table 1 also lists the maximum and minimum operating temperature for the various tubing materials.

In addition, Parker instrument fittings are designed to work on like materials. Stainless steel fittings should be used only with stainless steel tubing, aluminum fittings with aluminum tubing, etc. The practice of mixing materials is strongly discouraged. The only exception is brass fittings with copper tubing.

Dissimilar materials in contact may be susceptible to galvanic corrosion. Further, different materials have different levels of hardness, and can adversely affect the fittings ability to seal on the tubing.

Table 1

| Tubing Material | General Application | Recommended Temperature Range |
|-----------------------------------|--|---|
| Stainless Steel (Type 316) | High Pressure, High Temperature, Generally Corrosive Media | -425°F to 1,200°F1 (-255°C to 605°C) |
| Carbon Steel | High Pressure, High Temperature Oil, Air, Some Specialty Chemicals | -20°F to 800°F2 (-29°C to 425°C) |
| Copper | Low Temperature, Low Pressure Water, Oil, Air | -40°F to 400°F (-40°C to 205°C) |
| Aluminum | Low Temperature, Low Pressure Water, Oil, Air, Some Specialty Chemicals | -40°F to 400°F (-40°C to 205°C) |
| Monel® 400 | Recommended for Sour Gas Applications Well Suited for Marine and General Chemical Processing Applications | -325°F to 800°F (-198°C to 425°C) |
| Hastelloy® C-276 | Excellent Corrosion Resistance to Both Oxidizing and Reducing Media and Excellent Resistance to Localized Corrosion Attack | -325°F to 1000°F (-198°C to 535°C) |
| Carpenter® 20 | Applications Requiring Resistance to Stress Corrosion Cracking in Extreme Conditions | -325°F to 800°F (-198°C to 425°C) |
| Inconel® Alloy 600 | Recommended for High Temperature Applications with Generally Corrosive Media | -205°F to 1200°F (-130°C to 650°C) |
| Titanium | Resistant to Many Natural Environments such as Sea Water, Body Fluids and Salt Solutions | -75°F to 600°F (-59°C to 315°C) |

1. For operating temperatures above 800°F (425°C), consideration should be given to media. 300 Series Stainless Steels are susceptible to carbide precipitation which may lead to intergranular corrosion at elevated temperatures.

2. Consideration should be given to maximum temperature ratings if fittings and/or tubing are coated or plated. All temperature ratings based on temperatures per ASME B31.3 Chemical Plant and Petroleum Refinery Piping Code, 1999 Edition.

The information listed in Table 1 is general in scope. For specific applications, please contact Parker's Instrumentation Products Division, Product Engineering Department (256) 881-2040.

NOTE: Hastelloy® is a registered trademark of Haynes International. Inconel®, and Monel® are registered trademarks of Special Metals Corporation. Carpenter® is a registered trademark of CRS Holdings Inc.

Gas Service

Special care must be taken when selecting tubing for gas service. In order to achieve a gas-tight seal, ferrules in instrument fittings must seal any surface imperfections. This is accomplished by the ferrules penetrating the surface of the tubing. Penetration can only be achieved if the tubing provides radial resistance and if the tubing material is softer than the ferrules.

Thick walled tubing helps to provide resistance. Tables 2–7 indicate the minimum acceptable wall thickness for various materials in gas service. The ratings in white indicate combination of diameter and wall thickness which are suitable for gas service.

Acceptable tubing hardness for general application is listed in Table 9. These values are the maximum allowed by ASTM. For gas service, better results can be obtained by using tubing well below this maximum hardness. For example, a desirable hardness of 80 Rb is suitable for stainless steel. The maximum allowed by ASTM is 90 Rb.

System Pressure

The system operating pressure is another important factor in determining the type, and more importantly, the size of tubing to be used. In general, high pressure installations require strong materials such as steel or stainless steel. Heavy walled softer tubing such as copper may be used if chemical compatibility exists with the media. However, the higher strength of steel or stainless steel permits the use of thinner tubes without reducing the ultimate rating of the system. In any event, tube fitting assemblies should never be pressurized beyond the recommended working pressure.

The following tables (2–7) list by material the maximum suggested working pressure of various tubing sizes. Acceptable tubing diameters and wall thicknesses are those for which a rating is listed. Combinations, which do not have a pressure rating, are not recommended for use with instrument fittings.

Maximum Allowable Working Pressure Tables

| Table 2 316 or 304 Stainless Steel (Seamless) | | | | | | | | | | | | | | | | |
|---|----------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Tube O.D. Size | Wall Thickness | | | | | | | | | | | | | | | |
| | 0.010 | 0.012 | 0.014 | 0.016 | 0.020 | 0.028 | 0.035 | 0.049 | 0.065 | 0.083 | 0.095 | 0.109 | 0.120 | 0.134 | 0.156 | 0.188 |
| 1/16 | 5600 | 6900 | 8200 | 9500 | 12100 | 16800 | | | | | | | | | | |
| 1/8 | | | | | | 8600 | 10900 | | | | | | | | | |
| 3/16 | | | | | | 5500 | 7000 | 10300 | | | | | | | | |
| 1/4 | | | | | | 4000 | 5100 | 7500 | 10300 | | | | | | | |
| 5/16 | | | | | | | 4100 | 5900 | 8100 | | | | | | | |
| 3/8 | | | | | | | 3300 | 4800 | 6600 | | | | | | | |
| 1/2 | | | | | | | 2600 | 3700 | 5100 | 6700 | | | | | | |
| 5/8 | | | | | | | | 3000 | 4000 | 5200 | 6100 | | | | | |
| 3/4 | | | | | | | | 2400 | 3300 | 4300 | 5000 | 5800 | | | | |
| 7/8 | | | | | | | | 2100 | 2800 | 3600 | 4200 | 4900 | | | | |
| 1 | | | | | | | | | 2400 | 3200 | 3700 | 4200 | 4700 | | | |
| 1-1/4 | | | | | | | | | | 2500 | 2900 | 3300 | 3700 | 4100 | 4900 | |
| 1-1/2 | | | | | | | | | | | 2400 | 2700 | 3000 | 3400 | 4000 | 4500 |
| 2 | | | | | | | | | | | | 2000 | 2200 | 2500 | 2900 | 3200 |

| Table 3 316 or 304 Stainless Steel (Welded) | | | | | | | | | | | | | | | | |
|---|----------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Tube O.D. Size | Wall Thickness | | | | | | | | | | | | | | | |
| | 0.010 | 0.012 | 0.014 | 0.016 | 0.020 | 0.028 | 0.035 | 0.049 | 0.065 | 0.083 | 0.095 | 0.109 | 0.120 | 0.134 | 0.156 | 0.188 |
| 1/16 | 4800 | 5900 | 7000 | 8100 | 10300 | 14300 | | | | | | | | | | |
| 1/8 | | | | | | 7300 | 9300 | | | | | | | | | |
| 3/16 | | | | | | 4700 | 6000 | 8700 | | | | | | | | |
| 1/4 | | | | | | 3400 | 4400 | 6400 | 8700 | | | | | | | |
| 5/16 | | | | | | | 3400 | 5000 | 6900 | | | | | | | |
| 3/8 | | | | | | | 2800 | 4100 | 5600 | | | | | | | |
| 1/2 | | | | | | | 2200 | 3200 | 4300 | 5700 | | | | | | |
| 5/8 | | | | | | | | 2500 | 3400 | 4500 | 5200 | | | | | |
| 3/4 | | | | | | | | 2100 | 2800 | 3700 | 4200 | 4900 | | | | |
| 7/8 | | | | | | | | 1800 | 2400 | 3100 | 3600 | 4200 | | | | |
| 1 | | | | | | | | | 2100 | 2700 | 3100 | 3600 | 4000 | | | |
| 1-1/4 | | | | | | | | | | 2100 | 2400 | 2800 | 3100 | 3500 | 4200 | |
| 1-1/2 | | | | | | | | | | | 2000 | 2300 | 2600 | 2900 | 3400 | 4200 |
| 2 | | | | | | | | | | | | 1700 | 1900 | 2100 | 2500 | 3000 |

Instrument Tubing Selection Guide

| Table 4 Carbon Steel (Seamless) | | | | | | | | | | | | |
|---------------------------------|----------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Tube O.D. Size | Wall Thickness | | | | | | | | | | | |
| | 0.028 | 0.035 | 0.049 | 0.065 | 0.083 | 0.095 | 0.109 | 0.120 | 0.134 | 0.148 | 0.165 | 0.180 |
| 1/8 | 8100 | 10300 | | | | | | | | | | |
| 3/16 | 5200 | 6700 | 9700 | | | | | | | | | |
| 1/4 | 3800 | 4900 | 7100 | 9700 | | | | | | | | |
| 5/16 | | 3800 | 5500 | 7700 | | | | | | | | |
| 3/8 | | 3100 | 4500 | 6200 | | | | | | | | |
| 1/2 | | 2300 | 3300 | 4500 | 6000 | | | | | | | |
| 5/8 | | 1800 | 2600 | 3500 | 4600 | 5400 | | | | | | |
| 3/4 | | | 2200 | 2900 | 3800 | 4400 | 5100 | | | | | |
| 7/8 | | | 1800 | 2500 | 3200 | 3700 | 4300 | | | | | |
| 1 | | | 1600 | 2100 | 2800 | 3200 | 3700 | 4100 | | | | |
| 1-1/4 | | | | 1700 | 2200 | 2500 | 2900 | 3200 | 3700 | 3800 | | |
| 1-1/2 | | | | | 1800 | 2100 | 2400 | 2700 | 3000 | 3400 | 3800 | 4000 |
| 2 | | | | | | 1600 | 1800 | 2000 | 2200 | 2500 | 2800 | 3000 |

| Table 6 Aluminum (Seamless) | | | | | |
|-----------------------------|----------------|-------|-------|-------|-------|
| Tube O.D. Size | Wall Thickness | | | | |
| | 0.035 | 0.049 | 0.065 | 0.083 | 0.095 |
| 1/8 | 8700 | | | | |
| 3/16 | 5600 | 8100 | | | |
| 1/4 | 4100 | 5900 | | | |
| 5/16 | 3200 | 4600 | | | |
| 3/8 | 2600 | 3800 | | | |
| 1/2 | 1900 | 2800 | 3800 | | |
| 5/8 | 1500 | 2200 | 2900 | | |
| 3/4 | | 1800 | 2400 | 3200 | |
| 7/8 | | 1500 | 2100 | 2700 | |
| 1 | | 1300 | 1800 | 2300 | 2700 |

| Table 5 Copper (Seamless) | | | | | | | | | | |
|---------------------------|----------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Tube O.D. Size | Wall Thickness | | | | | | | | | |
| | 0.010 | 0.020 | 0.028 | 0.035 | 0.049 | 0.065 | 0.083 | 0.095 | 0.109 | 0.120 |
| 1/16 | 1700 | 3800 | 5400 | | | | | | | |
| 1/8 | | | 2800 | 3600 | | | | | | |
| 3/16 | | | 1800 | 2300 | 3500 | | | | | |
| 1/4 | | | 1300 | 1700 | 2600 | 3500 | | | | |
| 5/16 | | | | 1300 | 2000 | 2800 | | | | |
| 3/8 | | | | 1100 | 1600 | 2300 | | | | |
| 1/2 | | | | 800 | 1200 | 1600 | 2200 | | | |
| 5/8 | | | | | 900 | 1300 | 1700 | 2000 | | |
| 3/4 | | | | | 800 | 1000 | 1400 | 1600 | 1900 | |
| 7/8 | | | | | 600 | 900 | 1100 | 1300 | 1600 | |
| 1 | | | | | 600 | 800 | 1000 | 1200 | 1400 | 1500 |
| 1-1/8 | | | | | 500 | 700 | 900 | 1000 | 1200 | 1300 |
| 1-1/4 | | | | | | | 800 | 900 | 1100 | 1200 |
| 1-1/2 | | | | | | | 650 | 750 | 850 | 950 |

| Table 7 Monel 400 (Seamless) | | | | | | | | | | |
|------------------------------|----------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Tube O.D. Size | Wall Thickness | | | | | | | | | |
| | 0.010 | 0.020 | 0.028 | 0.035 | 0.049 | 0.065 | 0.083 | 0.095 | 0.109 | 0.120 |
| 1/16 | 5500 | 11800 | 16300 | | | | | | | |
| 1/8 | | | 8100 | 10400 | | | | | | |
| 3/16 | | | 5100 | 6600 | 9600 | | | | | |
| 1/4 | | | 3800 | 4800 | 7000 | 9600 | | | | |
| 5/16 | | | | 3800 | 5500 | 7500 | | | | |
| 3/8 | | | | 3100 | 4500 | 6100 | | | | |
| 1/2 | | | | 2300 | 3300 | 4500 | 5900 | | | |
| 5/8 | | | | | 2700 | 3700 | 4900 | 5600 | | |
| 3/4 | | | | | 2300 | 3100 | 4000 | 4600 | 5400 | |
| 1 | | | | | | 2300 | 2900 | 3400 | 3900 | 4400 |

- NOTE:** • All working pressures have been calculated using the maximum allowable stress levels in accordance with ASME B31.3, Chemical Plant and Petroleum Refinery Piping Code, 1999 Edition.
- All calculations are based on maximum outside diameter and minimum wall thickness.
 - All working pressures are ambient (72°F or 22°C) temperature.

System Temperature

Operating temperature is another factor in determining the proper tubing material. Copper and aluminum tubing are suitable for low temperature media. Stainless steel and carbon steel tubing are suitable for higher temperature media. Special alloys such as Alloy 600 are recommended for extremely high temperatures (see Table 1). Table 8 lists derating factors which should be applied to the working pressures listed in Tables 2–7 for elevated temperature conditions. Simply locate the correct factor in Table 8 and multiply this by the appropriate value in Tables 2–7 for elevated temperature working pressure.

| Table 8 Temperature Derating Factors | | | | | | | |
|--------------------------------------|-------|--------|----------|--------|--------|-------|-----------|
| Temperature | | Copper | Aluminum | 316 SS | 304 SS | Steel | Monel 400 |
| °F | (°C) | | | | | | |
| 100 | (38) | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 |
| 200 | (93) | .80 | 1.00 | 1.00 | 1.00 | .96 | .88 |
| 300 | (149) | .78 | .81 | 1.00 | 1.00 | .90 | .82 |
| 400 | (204) | .50 | .40 | .97 | .94 | .86 | .79 |
| 500 | (260) | | | .90 | .88 | .82 | .79 |
| 600 | (316) | | | .85 | .82 | .77 | .79 |
| 700 | (371) | | | .82 | .80 | .73 | .79 |
| 800 | (427) | | | .80 | .76 | .59 | .76 |
| 900 | (486) | | | .78 | .73 | | .43 |
| 1000 | (538) | | | .77 | .69 | | |
| 1100 | (593) | | | .62 | .49 | | |
| 1200 | (649) | | | .37 | .30 | | |

EXAMPLE: 1/2 inch x .49 wall seamless 316 stainless steel tubing has a working pressure of 3700 psi @ room temperature. If the system were to operate @ 800°F (425°C), a factor of 80% or (.80) would apply (see Table 8 above) and the “at temperature” system pressure would be 3700 PSI x .80 = 2960 PSI.



Tubing Ordering Suggestions

Tubing for use with Parker instrument fittings must be carefully ordered to insure adequate quality for good performance. Each purchase order must specify the material nominal outside diameter, and wall thickness. Ordering to ASTM specifications insures that the tubing will be dimensionally, physically, and chemically within strict limits. Also, more stringent requirements may be added by the user. All tubing should be ordered free of scratches and suitable for bending.

A purchase order meeting the above criteria would read as follows:

“1/2 x .049 316 stainless steel, seamless, or welded and redrawn per ASTM A-249. Fully annealed, 80 Rb or less. Must be suitable for bending; surface scratches, and imperfections (incomplete weld seams) are not permissible.”

Table 9 lists specific ordering information for each material.

| Table 9 | | | | |
|--------------------|---------------------------|--------------------------------|------------------------|---------------------------|
| Material | Type | ASTM Tubing Spec. | Condition | Max. Recommended Hardness |
| Stainless Steel | 304, 316, 316L | ASTM-A-269, A-249, A-213, A632 | Fully Annealed | 90 Rb |
| Copper | K or L | ASTM-B75 B68, B88 (K or L)* | Soft Annealed Temper 0 | 60 Max. Rockwell 15T |
| Carbon Steel | 1010 | SAE-J524b, J525b ASTM-A-179 | Fully Annealed | 72 Rb |
| Aluminum | Alloy 6061 | ASTM B-210 | T6 Temper | 56 Rb |
| Monel® 400 | 400 | ASTM B-165 | Fully Annealed | 75 Rb |
| Hastelloy® C-276 | C-276 | ASTM-B-622, B-626 | Fully Annealed | 90 Rb |
| Inconel® Alloy 600 | 600 | ASTM B-167 | Fully Annealed | 90 Rb |
| Carpenter® 20 | 20CB-3 | ASTM B-468 | Fully Annealed | 90 Rb |
| Titanium | Commercially Pure Grade 2 | ASTM B-338 | Fully Annealed | 99 Rb 200 Brinell Typical |

*B88 Copper Tube to be ordered non-engraved

NOTE: Hastelloy® is a registered trademark of Haynes International. Inconel®, and Monel® are registered trademarks of Special Metals Corporation. Carpenter® is a registered trademark of CRS Holdings Inc.